

ANCAMIDE[®] 2769

Curing Agent

DESCRIPTION

Ancamide 2769 curing agent is an innovative technology designed for use with liquid epoxy resin. Showing polyamide like properties it is also 100% solids, contains no plasticizer and exhibits very low viscosity. This allows for formulation of solvent free or high solids coatings with ultra low volatile organic components.

TYPICAL PROPERTIES

Property	Value	Unit	Method
Appearance	Clear amber liquid		
Colour	≤ 10	Gardner	ASTM D 1544
Viscosity @ 25°C	100-160	mPa.s	Brookfield RVTD, Spindle 4
Amine Value	400-440	mg KOH/g	Perchloric Acid Titration
Specific Gravity @ 21°C	0.97		
Equivalent	150	Wt/{H}	
Recommended use Level	65-80	PHR	With bisphenol-A based epoxy resin (EEW=190), 80 phr

BENEFITS

- Very low viscosity
- 100% solvent and plasticizer free
- Excellent compatibility with liquid epoxy resin
- No induction time
- Good through cure and appearance at 10°C
- Good corrosion resistance
- Adhesion to poorly prepared substrates

APPLICATIONS

- High solids and solvent free marine and maintenance coatings
- General protective coatings
- Tank and container coatings

SHELF LIFE

At least 24 months from the date of manufacture in the original sealed container at ambient temperature. Store away from excessive heat and humidity in tightly closed containers.

STORAGE AND HANDLING

Refer to the Safety Data Sheet for Ancamide 2769 curing agent.


TYPICAL HANDLING PROPERTIES*

Property	Value	Unit	Method
Gel Time @ 25°C	120	min	Techne GT-3 Gelation Timer, 150 g mix
Thin Film Set Time @ 25°C	9	h	ASTM D 5895 - BK Drying Recorder, Phase 3
Thin Film Set Time @ 10°C	24	h	ASTM D 5895 - BK Drying Recorder, Phase 3
Persoz Hardness 1/ 7d @ 25°C	205/ 300	s	ASTM D 4366
Typical cure schedule	2-7	days	

* With bisphenol-A based epoxy resin (EEW=190), 80 phr

SUPPLEMENTARY DATA

Ancamide 2769 provides enhanced adhesion to poorly prepared substrates. In this example, sandblasted steel SA2 ½ panels were prepared by immersing in water for 3-4 weeks until the rust build was significant. Then the panels were coated using standard LER (EEW=190) with Ancamide 2769 and tested for pull-off adhesion.


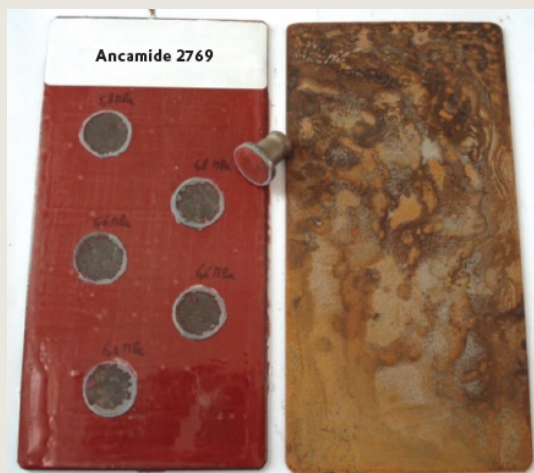


The adhesion was compared with a modified polyamide adduct and a modified polyamide for both wet concrete and metal. The results are shown below:

TABLE 3:

Curing Agent	Adhesion to Wet Concrete		Adhesion to Rusted Metal	
	Strength, PSI	Mode of failure	Strength, PSI	Mode of failure
Ancamide 2769	783	Concrete cohesive failure	899	Failure in the rust layer
Modified Polyamide Adduct	783	Concrete cohesive failure	928	Failure in the rust layer
Modified polyamide	493	100% delamination	—	—

Intercoat adhesion was also tested and shown to be superior to a polyamide adduct because the Ancamide 2769 does not contain plasticizer that can leach out during the drying process. The test was conducted according to ISO 2409, on panels with 2X100 micron DFT (~ 4 mils) thickness. The films were overcoated after 4 days of cure at ambient conditions.

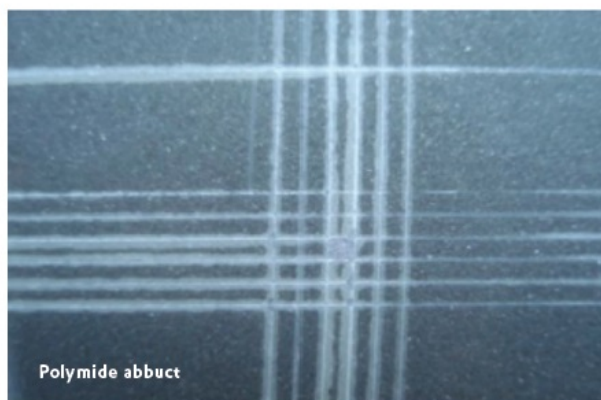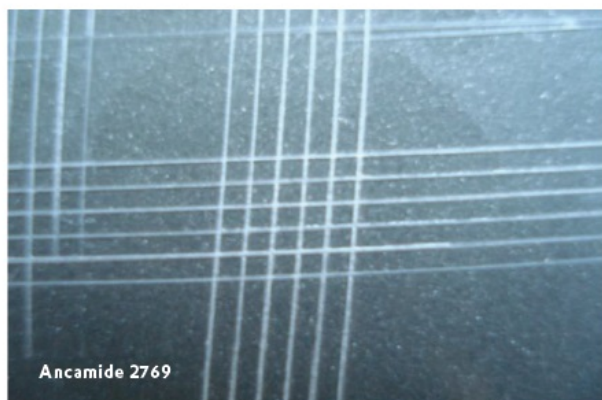

Result: GT 0

Result: GT 3

ISO 2409: GT 0 = best, GT 5 = worst

The Ancamide 2769 sample continued to maintain adhesion through 12 days at which point the test was terminated.

STARTING POINT FORMULATION: ANTICORROSIVE PRIMER

The following is offered as a starting point formulation for an anticorrosive primer application.

TABLE 4:

A-Component			Weight (lb)
Standard Bis-A LER (EEW=190)	Epoxy Resin	Various	31.4
Epodil® 742	Reactive diluent	Evonik	3.6
ZetaSpers® 2100 agent	Dispersing agent	Evonik	1.0
BYK 57	Defoamer	BYK	1.0
Bayferrox 130M	Pigment	Bayer	5.0
Plastorit 000	Filler	Kremer	15.0
Sachtleben Micro	Filler	Sachtleben	26.0
Heucophos ZCP-plus	Anti-corrosive pigment	Heubach	6.7
10 ES Wollastocoat	Filler	NYCO Minerals	10.0
Bentone SD-2	Rheology modifier	Elementis	0.3
Xylene/Butanol (4:1)	Solvent	Various	6.8
Total A			106.8
B-Component			
Ancamide 2769	Curing agent	Evonik	28.2

Please note that early hot water resistance (60°C) can be improved by adding a co-curing agent such as Ancamine 2739 to the B-side at a 70/30 to 50/50 mix of 2769/ 2739. The properties and performance of this formulation can be seen in Table 5.

TABLE 5: ANTICORROSIVE PRIMER USING ANCAMIDE 2769

Property	Unit	Value
VOC	g/L	85
PVC	%	23
Mix viscosity	mPa.s (cPs)	1000
Mix solids	Vol. %	91
Mix ratio (weight)	A:B	3.8:1
Mix ratio (volume)	A:B	2:1
Potlife (min. to double viscosity)	23°C	90-120
TFST, 74°F (23°C)	Phase 2	9.0
150µm wft (6 mil)	Phase 3	13.0
TFST, 50°F (10°C)	Phase 2	19.0
150µm wft (6 mil)	Phase 3	27.0
Persoz Hardness, 74°F (23°C)	24 h	87
	7 d	164
	14 d	179
Persoz Hardness, 50°F (10°C)	24 h	soft
	7 d	76
	14 d	108
Gloss, 74°F (23°C)	20°/ 60°	85/ 97
Salt Spray 2000 h	Field/ Scribe	10/ 9*
Prohesion 2000 h	Field/ Scribe	10/ 9*
Cleveland Humidity	12 months	No loss of adhesion, No blisters

*rating 10 = best (no blisters or corrosion)

Ancamide® is a registered trademark of Evonik Industries AG or one of its subsidiaries.

Disclaimer

This information and any recommendations, technical or otherwise, are presented in good faith and believed to be correct as of the date prepared. Recipients of this information and recommendations must make their own determination as to its suitability for their purposes. In no event shall Evonik assume liability for damages or losses of any kind or nature that result from the use of or reliance upon this information and recommendations. EVONIK EXPRESSLY DISCLAIMS ANY REPRESENTATIONS AND WARRANTIES OF ANY KIND, WHETHER EXPRESS OR IMPLIED, AS TO THE ACCURACY, COMPLETENESS, NON-INFRINGEMENT, MERCHANTABILITY AND/OR FITNESS FOR A PARTICULAR PURPOSE (EVEN IF EVONIK IS AWARE OF SUCH PURPOSE) WITH RESPECT TO ANY INFORMATION AND RECOMMENDATIONS PROVIDED. Reference to any trade names used by other companies is neither a recommendation nor an endorsement of the corresponding product, and does not imply that similar products could not be used. Evonik reserves the right to make any changes to the information and/or recommendations at any time, without prior or subsequent notice.

EVONIK OPERATIONS GMBH

Business Line Crosslinkers
Paul-Baumann-Str. 1
45764 Marl
Germany

www.evonik.com/crosslinkers

Product Information: APCSE@evonik.com

Sample Request: APCSE@evonik.com

EVONIK CORPORATION

Business Line Crosslinkers
7001 Hamilton Boulevard
Trexlerstown, PA 18087
USA

CrosslinkersProinfo@evonik.com

Crosslinkers-Samples@evonik.com

**EVONIK SPECIALTY CHEMICALS
(SHANGHAI) CO., LTD.**

Business Line Crosslinkers
55, Chungong Road
Xinzhuang Industry Park
Shanghai, 201108
China

CL-Asiainfo@evonik.com

CL-Asiainfo@evonik.com

