

**ANCAMINE<sup>®</sup> 2280****Curing Agent****DESCRIPTION**

Ancamine 2280 curing agent is a low-viscosity modified cycloaliphatic amine designed for use with liquid epoxy resins in two-package formulations. It yields formulations with excellent chemical resistance, waterspot resistance and resistance to amine blush. These properties make Ancamine 2280 ideal for formulating flooring, coatings and linings.

**TYPICAL PROPERTIES**

Property	Value	Unit	Method
Appearance	Amber Liquid		
Color	8	Gardner	ASTM D 1544-80
Viscosity @ 77°F	450	cP	ASTM D-445-83, Brookfield, RVTD, Spindle 4
Amine Value	250	mg KOH/g	Perchloric Acid Titration
Specific Gravity @ 70°F	1.06		ASTM D 1475-85
Flash Point (closed cup)	>200	°F	Seta Flash Closed Cup
Equivalent Wt/{H}	110		
Recommended use Level	58	phr	EEW=182

**ADVANTAGES**

- Excellent resistance to amine blush and waterspotting at ambient and low temperatures
- Excellent chemical resistance
- Good low-temperature cure
- Low skin irritation — DOT noncorrosive

**APPLICATIONS**

- Industrial flooring
- High-solids coatings
- Chemically resistance linings and mortars
- Secondary containment linings

## SHELF LIFE

At least 24 months from the date of manufacture in the original sealed container at ambient temperature. Store away from excessive heat and humidity in tightly closed containers.

## STORAGE AND HANDLING

Refer to the Safety Data Sheet for Ancamine 2280 curing agent.

## TYPICAL CURE SCHEDULE

**7 days at ambient temperature**

## TYPICAL HANDLING PROPERTIES\*

Property	A*	B*	Unit	Method
Use Level	58	55.9	phr	
Mixed Viscosity @ 77°F	2,860	1,240	cP	ASTM D-445-83, Brookfield RVTD, Spindle 4
Gel Time (150g mix @ 77°F)	50	79	min	Techne GT-4 Gelation Timer
(150g mix @ 50°F)	113	235	min	Techne GT-4 Gelation Timer
Thin Film Set Time @ 77°F	6.0	8.8	h	BK Drying Recorder
@ 50°F	13	22.5	h	BK Drying Recorder
@ 40°F	19	29	h	BK Drying Recorder
Peak Exotherm (150g mix @ 77°F)	250	-		ASTM D 2471-71

\* Liquid Resin Suppliers: Epon 828 Resin™: Shell Chemical Company. Epon 862 Resin™, Shell Chemical Company. D.E.R. 331 Resin™, Dow Chemical Company. D.E.N. 431 Resin™, Dow Chemical Company.

A\* Ancamine 2280 formulated with standard Bisphenol-A (DGEBA, EEW = 190) epoxy resin.

B\* Ancamine 2280 with 90% DGEBA resin (EEW = 190) and 10% Epodil® 748 diluent (C<sub>12</sub>-C<sub>14</sub> alkyl glycidyl ether).



## TYPICAL PERFORMANCE\* (7 DAY CURE @ 77°F)

Property	A*	B*	Unit	Method
Glass Transition Temperature	122	-	°F	ASTM D 3418-82
Compressive Strength @ yield	10,400	6,900	psi	ASTM D 695-85
Compressive Modulus	307	231	thousand psi	ASTM D 695-85
Tensile Strength	7,600	4,900	psi	ASTM D 638-86
Tensile Modulus	390	218	thousand psi	ASTM D 638-86
Tensile Elongation @ break	3.2	12	%	ASTM D 638-86
Flexural Strength	13,600	9,700	psi	ASTM D 790-86
Flexural Modulus	500	303	thousand psi	ASTM D 790-86
Hardness	78	78	Shore D	ASTM D 2240-86
60° Specular Gloss	104	-		ASTM D 523-85
Abrasion Resistance Weight Loss (@ 1,000 cycles with wheel no. 10)	-	0.052	grams	ASTM D 4060-90
Mar Resistance	-	1.05	kg	ASTM D 5178-91

## SUPPLEMENTAL DATA

### EXCELLENT WATERSPOTTING RESISTANCE

Curing agents were combined at recommended mix ratios with standard liquid epoxy resin (EEW=190). 10 mil films were applied to steel Q panels and cured at 40°F, 90% RH. After 18, 24, 36, 48 and 72 hours, water saturated cotton was placed on each film for 24 hours. The coatings were then evaluated for waterspottling resistance.

As shown in Figure 1, Ancamine 2280 curing agent provides excellent waterspottling resistance, superior to standard cycloaliphatic amine curing agents. It rapidly develops resistance to amine blush and exudation, even when cured at reduced temperature (40°F) and high humidity (90% RH).


\* Liquid Resin Suppliers: Epon 828 Resin™: Shell Chemical Company. Epon 862 Resin™, Shell Chemical Company. D.E.R. 331 Resin™, Dow Chemical Company. D.E.N. 431 Resin™, Dow Chemical Company.

A\* Ancamine 2280 formulated with standard Bisphenol-A (DGEBA, EEW = 190) epoxy resin.

B\* Ancamine 2280 with 90% DGEBA resin (EEW = 190) and 10% Epodil® 748 diluent (C<sub>12</sub>-C<sub>14</sub> alkyl glycidyl ether).



FIGURE 1: WATERSPOTTING RESISTANCE OF CYCLOALIPHATIC AMINE CURING AGENTS

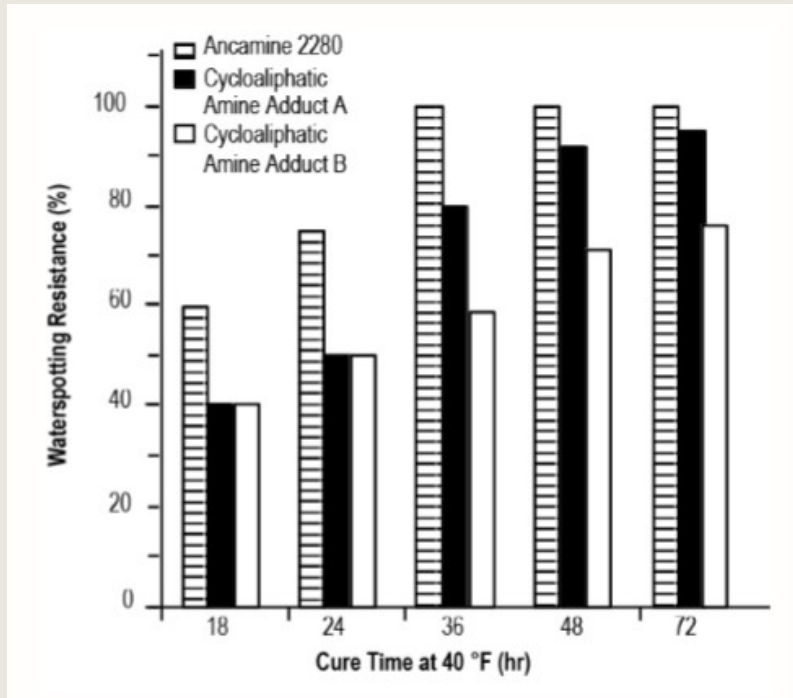

**EXCELLENT CHEMICAL RESISTANCE - IMMERSION RESISTANCE:** Chemical immersion studies following ASTM D543 were performed on coupons using standard bisphenol-A (EEW=190) resin and bisphenol-F (EEW=170) resin. Ancamine 2280 and three industry standard curing agents were mixed with the resins at recommended use levels and cured for 7 days at 77°F. The coupons were then immersed in the reagents at 77°F and percent weight gain was measured after specified time periods. A lower weight gain generally indicates better chemical resistance.

As shown in Table 4, Ancamine 2280 curing agent, when combined with bisphenol-A epoxy, provides excellent chemical resistance to many typical solvents, acids and bases. And, data in Table 5 shows chemical resistance of Ancamine 2280 curing agent can be enhanced with the use of bisphenol-F epoxy in applications requiring improved chemical resistance.

Chemical resistance of Ancamine 2280-cured formulations can be further optimized for specific chemicals using different resin blends. Table 6 shows immersion data for Ancamine 2280 with a bisphenol-F/multifunctional epoxy novolac resin blend.

Ancamine 2280 curing agent imparts outstanding chemical resistance with this resin blend to all of the reagents except MEK.

Another advantage of Ancamine 2280 curing agent is that it offers formulating flexibility for chemical resistance depending on the specific chemical environment. To demonstrate this, Ancamine 2280 was mixed with bisphenol-A epoxy (EEW=190) at 53, 58 and 63 phr. Samples were cured for 7 days at ambient temperature before immersion.

As shown in Figure 2, higher use of Ancamine 2280 improves hydrocarbon resistance, while lower use levels improve aqueous acid resistance. At all use levels, resistance to water is good.

TABLE 4: COMPARATIVE CHEMICAL RESISTANCE\*\* WITH BISPHENOL-A EPOXY RESIN - PERCENT WEIGHT GAIN

Reagent	Immersion Time	Ancamine 2280	Cycloaliphatic Mannich Base	Cycloaliphatic Amine Adduct C	Cycloaliphatic Amine Adduct D
<b>Xylene</b>	3 week	0.1	0.4	1.0	2.3
	3 month	0.01	0.9	-1.0	10.1
<b>Toluene</b>	3 week	2.3	3.3	6.6	29.2
	3 month	6.5	11.8	17.3	Destroyed
<b>Trichlorethane</b>	3 week	0.1	0.0	0.3	1.2
	3 month	0.1	0.0	0.5	4.5
<b>Ethylene Glycol Monobutyl Ether</b>	3 week	2.4	6.5	2.5	6.2
	3 month	5.1	13.5	5.5	10.5
<b>Methyl Ether Ketone</b>	3 week	Destroyed	Destroyed	Destroyed	Destroyed
	3 month	Destroyed	Destroyed	Destroyed	Destroyed
<b>Ethanol</b>	3 week	6.98	10.7	5.0	5.2
	3 month	3.5	5.8	3.2	9.7
<b>Skydrol</b>	3 week	-0.3	-0.1	-0.3	-
	3 month	-0.7	-0.3	-0.8	-
<b>D.I. Water</b>	3 week	1.2	0.9	1.1	0.8
	3 month	1.7	1.7	1.6	1.7
<b>10% Acetic Acid</b>	3 week	5.4	5.0	4.6	12.2
	3 month	9.6	9.1	8.2	22.0
<b>5% Acetic Acid</b>	3 week	2.6	2.1	2.8	4.0
	3 month	4.4	3.6	4.8	7.6
<b>10% Lactic Acid</b>	3 week	1.9	2.5	1.7	8.7
	3 month	3.4	4.6	2.9	16.4
<b>70% Sulfuric Acid</b>	3 week	0.2	0.2	0.0	1.0
	3 month	0.2	0.1	-0.1	1.9
<b>50% NaOH</b>	3 week	-0.2	-0.2	-0.2	-0.1
	3 month	-0.2	-0.3	-0.3	-0.1

\*\*ASTM D 543

TABLE 5: COMPARATIVE CHEMICAL RESISTANCE\*\* WITH BISPHENOL-F EPOXY RESIN - PERCENT WEIGHT GAIN

Reagent	Immersion Time	Ancamine 2280	Cycloaliphatic Mannich Base	Aliphatic Amine Mannich Base
<b>98% Sulfuric Acid</b>	1 day	1.2	1.5	-0.5
	1 week	1.3	-0.2	-7.1
	3 week	-0.1	-1.8	-16.4
	3 month	-2.0	-3.8	-48.5
<b>Toluene</b>	1 day	0	-	0.0
	1 week	0.6	-	0.0
	3 week	1.3	-	0.1
	3 month	2.4	-	0.4
<b>Ethanol</b>	1 day	1.4	-	0.5
	1 week	3.5	-	1.3
	3 week	6.0	-	2.5
	3 month	2.4	-	4.9
<b>25% Acetic Acid</b>	1 day	3.1	3.1	10.1
	1 week	8.7	9.3	29.6
	3 week	16.2	16.0	Destroyed
	3 month	25.6	24.7	Destroyed

\*\*ASTM D 543



**SPILLAGE RESISTANCE:** Spillage resistance studies were conducted on Ancamine 2280 curing agent formulated with a 90% bisphenol-A resin (EEW=190) and 10% Epodil 748 diluent (C<sub>12</sub>-C<sub>14</sub> alkyl glycidyl ether) blend cured for 7 days at 77°F. Table 7 shows the immersion/recovery schedule for the testing. Percentage weight change and Shore D hardness were measured after each of the immersion periods. The samples were then allowed to recover before reimmersion for the next time period. Hardness retention is relevant in flooring applications where it indicates the ability of the floor to support traffic after exposure to chemical spills. Results of this study are presented in Table 8. These results show that Ancamine 2280 is very suitable for flooring systems that require high resistance to a variety of chemicals.

For information on chemical resistance of many other Evonik curing agents, please refer to our bulletin “Chemical Resistance for Ambient Cure Epoxy Formulations.”

TABLE 6: CHEMICAL RESISTANCE FOR ANCAMINE 2280 WITH BISPHENOL-F/ NOVOLAC RESIN BLEND - % WEIGHT CHANGE AS A FUNCTION OF TIME - CONTINUOUS IMMERSION

Reagent	3 day % Weight Change	28 day % Weight Change
Deionized Water	0.55	1.61
Methanol	8.94	8.76
Ethanol	1.92	5.19
Toluene	0.05	0.56
Xylene	0.00	0.09
Butyl Cellosolve	0.25	0.97
MEK	15.70	D@5
10% Lactic Acid	1.06	3.35
10% Acetic Acid	2.25	6.64
70% Sulfuric Acid	0.03	0.08
98% Sulfuric Acid	0.46	-1.63
50% Sodium Hydroxide	-0.01	-0.04
10% Sodium Hypochlorite	0.55	1.24
1,1,1 Trichloroethane	0.07	0.35

NOTE: Samples were cured for 7 days at 77°F before testing. Tested in accordance with ASTM D543-84. Bisphenol-F / Novolac Resin blend tested is 60 wt.% Epon 862 (EEW=172) and 40 wt.% D.E.N. 431 (EEW=176).





FIGURE 2: CHEMICAL RESISTANCE CAN BE IMPROVED BY ADJUSTING MIX RATIO

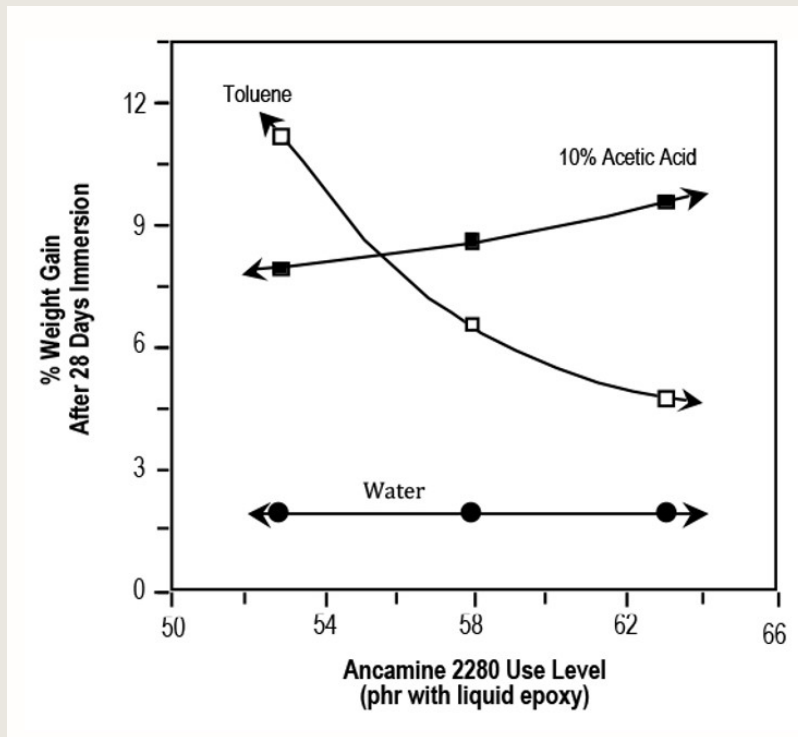


TABLE 7: SPILLAGE RESISTANCE TEST METHOD SCHEDULE

- Castings of 1/8" thickness are immersed for specified time period.
- Sample is then removed, weighed, and hardness tested immediately.
- Sample is then allowed to recover for specified time before re-immersion.

3 hr imm → test → 24 hr recover →  
 24 hr imm → test → 24 hr recover →  
 3 day imm → test → 3 day recover →  
 7 day imm → test → 7 day recover →  
 28 day imm → test → 7 day recover →  
 90 day imm → test

TABLE 8: SPILLAGE RESISTANCE FOR ANCAMINE 2280 WITH 90% DGEBA / 10% EPODIL 748 % WEIGHT CHANGE AND SHORE D HARDNESS AS A FUNCTION OF TIME

Reagent	Initial		After 3 hr		After 24 hr		After 3 days		After 7 days		After 28 days		After 90 days	
	Hard	% wt.	Hard	% wt.	Hard	% wt.	Hard	% wt.	Hard	% wt.	Hard	% wt.	Hard	% wt.
10% Acetic Acid	78	0.64	77	1.47	76	2.68	74	4.10	73	6.86	68	10.9	65	
10% Lactic Acid	78	0.16	78	0.47	79	1.05	77	1.66	78	2.72	76	4.00	65	
Toluene	78	0.09	75	2.62	69	8.79	65	11.48	57	13.39	50	18.09	50	
Xylene	78	-0.02	75	-0.01	74	0.69	70	1.92	64	6.50	62	8.51	62	
Trichloroethane	78	0.09	75	1.43	74	6.03	69	10.04	67	18.83	63	29.61	60	
Methanol	78	2.38	62	6.66	33	5.25	28	DESTROYED						
Ethanol	78	0.63	76	1.89	70	3.62	65	5.79	61	2.91	56	-1.04	68	
Butyl Cellosolve	78	0.17	75	0.85	71	2.20	64	3.41	63	6.78	60	14.42	60	
MEK	78	5.77	58	19.67	19	12.57	20	DESTROYED						
Skydrol	78	0.04	75	-0.06	75	-0.14	75	-0.23	74	-0.39	76	-0.55	53	
70% Sulfuric Acid	78	0.13	80	0.04	80	0.03	80	0.03	81	-0.01	80	0.0	80	
98% Sulfuric Acid	78	-19.33	72	DESTROYED										
Deionized Water	78	0.14	78	0.35	78	0.63	78	1.00	78	1.46	77	1.31	77	
50% Sodium Hydroxide	78	0.03	80	-0.05	78	-0.12	78	-0.16	78	-0.30	80	-0.44	63	
Bleach	78	0.08	79	0.31	78	0.57	79	0.81	78	0.82	79	0.26	64	

NOTE: Samples were cured for 7 days at 77°F before testing.

**CURE SPEED:** Thin film set times are shown in Figure 3 for Ancamine 2280 accelerated with Ancamine 1856, 2089M, 2205, or 2432 curing agents. 80% by weight Ancamine 2280 and 20% of the accelerating curing agents were mixed with standard bisphenol-A (DGEBA, EEW=190) resin at recommended use ratios. Three mil films were applied to glass plates and measured with a BK dry time recorder. At 77°F, accelerating Ancamine 2280 decreases thin film set time from 6 hours to 4.5 hours or less with all four products. These accelerators offer the capability to formulate Ancamine 2280 to the desired set time and still obtain good chemical resistance and waterspot resistance. Ancamine 2432 should be used as the accelerator for maximum chemical resistance.

As temperature decreases, use of the accelerators improves cure speed by about 40% compared to straight Ancamine 2280. Although all four accelerators will not severely impact blush resistance at a 20% use level, Ancamine 2089M or Ancamine 2432 should be used to maintain excellent blush resistance at low temperatures.

**FIGURE 3: CURE SPEEDS OF ACCELERATED ANCAMINE 2280 SYSTEMS**

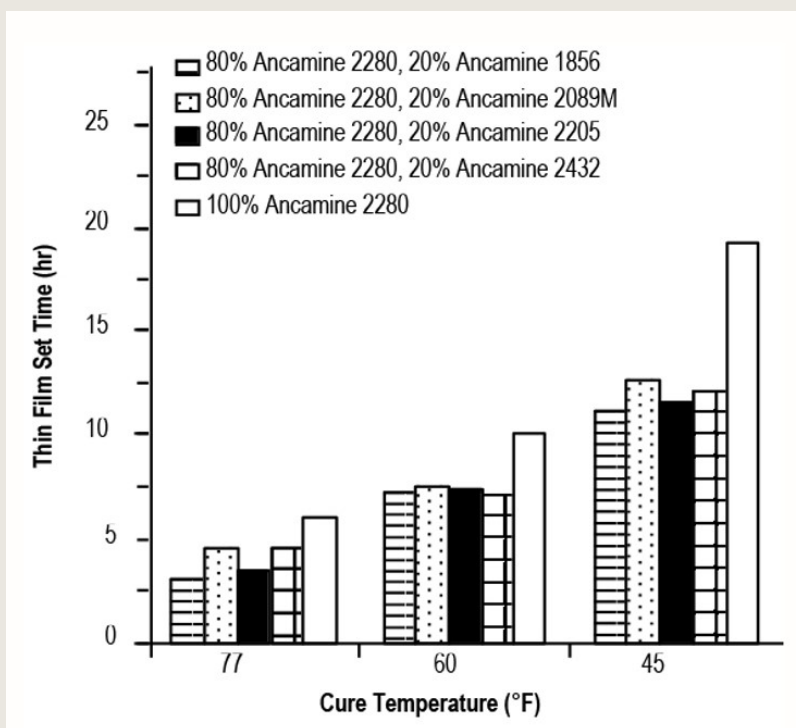


TABLE 9: HIGH-BUILD GRAY ENAMEL STARTING POINT FORMULATION

Component A	Parts by Weight	Method
Liquid DGEBA (EEW=190)*	450 lb	
Cresyl Glycidyl Ether (Epodil 742-Evonik)	100 lb	
Titanium Dioxide (DuPont)	150 lb	
Black Iron Oxide (Bayer)	2.0 lb	
Nuoperse 657 (Elementu)	1.5 lb	
Byk 320 (Byk Chemie)	1.0 lb	
FC 430 (3M Company)	0.6 lb	
	705.1 lb	
Component B		
Ancamine 2280	303 lb	
Mixed Properties		
Mixed Viscosity (KU)	110	ASTM D 562-81
Pot Life (min) (150 g mass)	75	Techne GT-4 Gelation Timer
Thin Film Set Time @ 77°F (hr)	6.5	BK Drying Recorder
Pounds per Gallon	9.9	ASTM D 1475-85
PVC (%)	4.5	
Hegman Grind	6+	ASTM D 1210-79
CURED FILM PROPERTIES – 7 DAY AMBIENT CURE		
Pencil Hardness	HB	ASTM D 6633
Gloss 60°	105	ASTM D 523-85
Cross Hatch Adhesion	5B	ASTM D 3359-87
MEK Double Rubs	200+	

\* Liquid Resin Suppliers: Epon 828 Resin™: Shell Chemical Company. Epon 862 Resin™, Shell Chemical Company. D.E.R. 331 Resin™, Dow Chemical Company. D.E.N. 431 Resin™, Dow Chemical Company.

**STARTING FORMULATION:** Table 9 shows a high-build gray enamel formulation using Ancamine 2280 curing agent.



Ancamine® is a registered trademark of Evonik Industries AG or one of its subsidiaries.

**Disclaimer**

This information and any recommendations, technical or otherwise, are presented in good faith and believed to be correct as of the date prepared. Recipients of this information and recommendations must make their own determination as to its suitability for their purposes. In no event shall Evonik assume liability for damages or losses of any kind or nature that result from the use of or reliance upon this information and recommendations. EVONIK EXPRESSLY DISCLAIMS ANY REPRESENTATIONS AND WARRANTIES OF ANY KIND, WHETHER EXPRESS OR IMPLIED, AS TO THE ACCURACY, COMPLETENESS, NON-INFRINGEMENT, MERCHANTABILITY AND/OR FITNESS FOR A PARTICULAR PURPOSE (EVEN IF EVONIK IS AWARE OF SUCH PURPOSE) WITH RESPECT TO ANY INFORMATION AND RECOMMENDATIONS PROVIDED. Reference to any trade names used by other companies is neither a recommendation nor an endorsement of the corresponding product, and does not imply that similar products could not be used. Evonik reserves the right to make any changes to the information and/or recommendations at any time, without prior or subsequent notice.

**EVONIK OPERATIONS GMBH**

Business Line Crosslinkers  
Paul-Baumann-Str. 1  
45764 Marl  
Germany

[www.evonik.com/crosslinkers](http://www.evonik.com/crosslinkers)

**Product Information:** [APCSE@evonik.com](mailto:APCSE@evonik.com)

**Sample Request:** [APCSE@evonik.com](mailto:APCSE@evonik.com)

**EVONIK CORPORATION**

Business Line Crosslinkers  
7001 Hamilton Boulevard  
Trexlerstown, PA 18087  
USA

[CrosslinkersProinfo@evonik.com](mailto:CrosslinkersProinfo@evonik.com)

[Crosslinkers-Samples@evonik.com](mailto:Crosslinkers-Samples@evonik.com)

**EVONIK SPECIALTY CHEMICALS  
(SHANGHAI) CO., LTD.**

Business Line Crosslinkers  
55, Chundong Road  
Xinzhuang Industry Park  
Shanghai, 201108  
China

[CL-Asiainfo@evonik.com](mailto:CL-Asiainfo@evonik.com)

[CL-Asiainfo@evonik.com](mailto:CL-Asiainfo@evonik.com)

